







Cadenza CX-C18

100 x 3 mm

HPLC COLUMN APPLICATION

LC-MS: PPDs and HMMM (rubber additives)

ゴム添加剤の LC-MS 分析

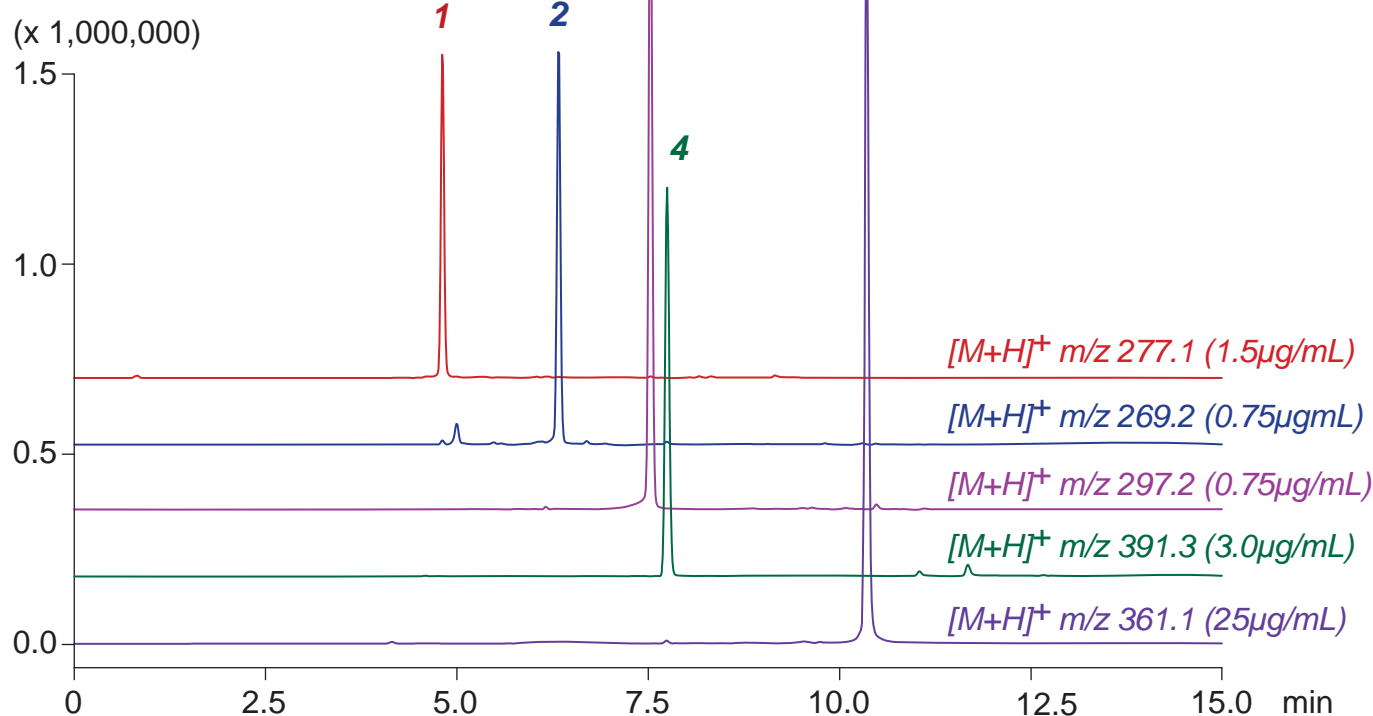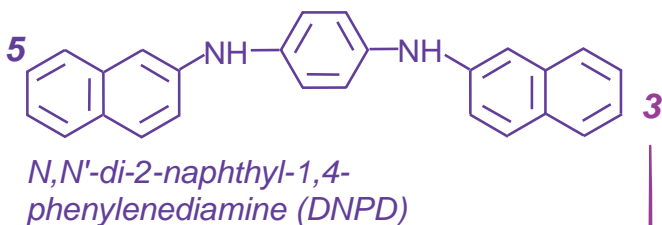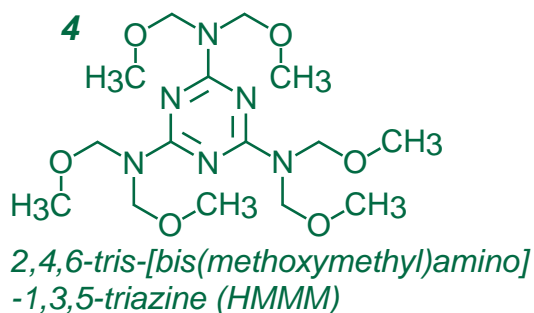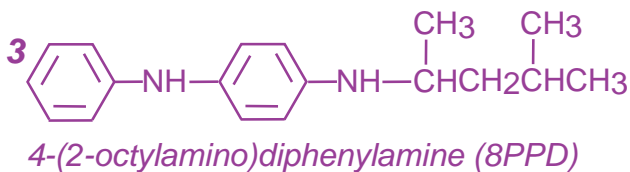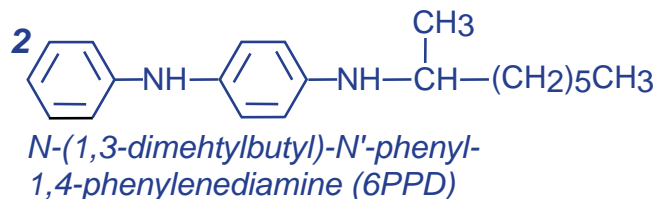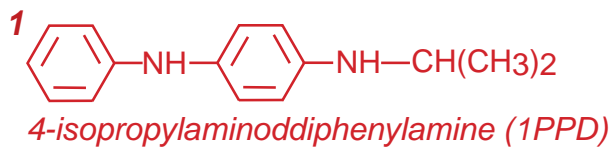

Cadenza CX-C18, 100 x 3 mm
 A: water / formic acid = 100 / 0.1
 B: acetonitrile / formic acid = 100 / 0.1
 0%B (0-1min), 0-60%B (1-7min), 100%B (7-15min)
 0.4mL/min (7MPa), 37°C, Single Quad. MS (ESI)
 5µL (0.75-25µg/mL, DMF / 100mM HCOONH₄ = 90 / 10)